

# PRO-SET®

## Technical Data

# INF-114

# INF-211

## INFUSION EPOXY

The New  
Standard

EPOXIES for  
Laminating  
Infusion  
Tooling  
Assembly

### Wessex Resins & Adhesives

Cupernham House  
Cupernham Lane  
Romsey, Hampshire  
SO51 7LF, UK  
pro-set.co.uk  
+44(0)1794 521111

ISO9001:2008 Certified

REV 1 / July 2013

©2013 Wessex Resins  
& Adhesives

### COMBINED FEATURES

**Very low viscosity** for rapid saturation of fibreglass, Kevlar and carbon fibre laminate with resin infusion and VARTM processes.

**Medium cure speed** hardener provides 3 to 4 hours of working time at 25°C. A typical laminate will be gelled in 8 hours.

**This combination** is formulated specifically for resin infusion and VARTM processes. Do not use in open mould applications.

**Room temperature cure** properties suitable for many composite components and structures.

**Tg as high as 91°C** with proper post cure providing excellent temperature stability and great part cosmetics.

**Cost Effective - High Performance** epoxy formulation for synthetic composite manufacturing.

### HANDLING PROPERTIES

Property	Standard	Units	21°C	25°C	29°C
150g Pot Life	ASTM D2471	minutes	131	122	72
500g Pot Life	ASTM D2471	minutes	101	85	63
Viscosity Mixed	ASTM D2196	mPas	296	245	196
Viscosity (resin)	ASTM D2196	mPas	1433		
Viscosity (hardener)	ASTM D2196	mPas	14		


### MIX RATIO

Method	Resin:Hardener	Resin:Hardener
Weight	3.65:1	100:27.4
Weight Range	3.81:1-3.45:1	100:26.3-100:29.0
Volume	3.00:1	100:33.3
Volume Range	3.13:1-2.84:1	100:31.9-100:35.3

### DENSITY

State	Units	21°C
Cured	gcm <sup>-3</sup>	1.14
Resin	gcm <sup>-3</sup>	1.14
Hardener	gcm <sup>-3</sup>	0.93

### VISCOSITY VS TEMPERATURE

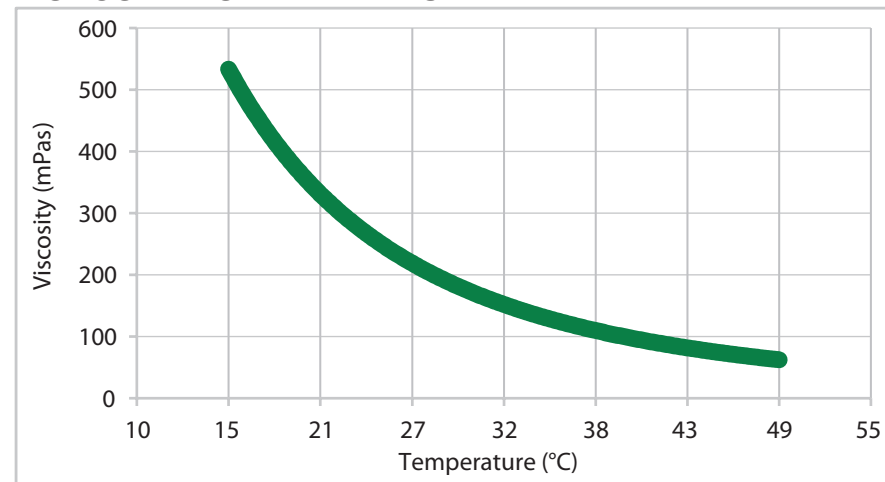

Test specimens were neat epoxy (without fibre reinforcement).  
Typical values not to be construed as specification

# INF-114 / INF-211

## INFUSION EPOXY

### MECHANICAL PROPERTIES

Property	Standard	Units	22°C x 4 Weeks	25°C x 2 Weeks	RT Gelation + 49°C x 8 hrs	RT Gelation + 60°C x 8 hrs	RT Gelation + 82°C x 8 hrs
Hardness	ASTM D2240	Shore D	86	86	85	85	85
Compression Yield	ASTM D895	MPa	101	105	94	94	94
Tensile Strength	ASTM D638	MPa	54	59	66	68	70
Tensile Modulus	ASTM D638	GPa	3.61	3.68	3.69	3.52	3.36
Tensile Elongation	ASTM D638	%	1.7	2.0	2.6	3.9	5.3
Flexural Strength	ASTM D790	MPa	85	103	118	121	125
Flexural Modulus	ASTM D790	GPa	3.34	3.33	3.43	3.41	3.2

### THERMAL PROPERTIES

Property	Standard	Units	22°C x 4 Weeks	25°C x 2 Weeks	RT Gelation + 49°C x 8 hrs	RT Gelation + 60°C x 8 hrs	RT Gelation + 82°C x 8 hrs	
Tg DMA Peak Tan Delta	ASTM E1640*1	°C	70	70	80	91	102	
Tg DMA Onset Storage Modulus	ASTM E1640*1	°C	63	63	69	80	91	
Tg DSC Onset - 1st Heat	ASTM E1356	°C	59	59	66	74	81	
Heat Deflection Temperature	ASTM D648	°C	54	55	62	71	78	
Tg DSC Ultimate	ASTM E1356	°C	85*2					

\*1 1Hz, 3°C per minute.

\*2 Additional post cure may be required; contact Technical Department for details.

Test specimens were neat epoxy (without fibre reinforcement).

These are typical properties and cannot be construed as a specification. The end users should test the products to ensure the products are suitable for the intended application. Any information, data, advice or recommendation published by Wessex Resins or obtained from Wessex Resins by other means and whether relating to Wessex Resins' materials or other materials, is given in good faith and believed to be reliable.

REV 1 / July 2013